

APPLICATION NOTE

Test for Switching Coefficients

Introduction

The rectangular loop property that is exhibited by certain microwave ferrimagnets is used in the design of a number of digital or latching ferrite phase shifters. The *Test for Hysteresis Loop Properties Application Note* (Document Number 202870) describes a measurement technique to obtain the coercive force (H_c), remanent flux density (B_r), and squareness ratio (R_s) of rectangular loop ferrimagnets. Another useful parameter of these materials, obtained experimentally as a constant of proportionality between magnetizing force and speed of magnetic flux reversal, is known as the switching coefficient (S_w).

The time required for the magnetic flux to switch from $-B_r$ to $+B_r$ in a toroidal core is inversely proportional to the magnetizing field (H), for amplitudes of H greater than approximately twice the coercive force. Theory suggests that the magnetic dipoles are reversed or switched in this region by a non-uniform rotation mechanism. A convenient method of measuring the switching coefficient is described in "Measurement" on page 2.


Oscilloscope Method

Figure 1 shows a typical measuring circuit. Three separate coils are placed around a thin-walled toroidal specimen and comprise of a:

- Block winding through which a $10\ \mu\text{s}$ duration current pulse (i_b) of constant amplitude, equal to about 10 times the specimen coercive force, is passed.
- Read winding for a $10\ \mu\text{s}$ duration current pulse (i_r), controllable in amplitude from about 1-to-10 times the specimen coercive force.
- Readout winding to obtain the output voltage waveform on a Cathode Ray Oscilloscope (CRO) screen at point A; or if followed by an integrating network, to obtain the magnetic flux waveform at point B.

Alternate block and read pulses are applied approximately 100 times per second. As the read pulse magnitude is varied, the switching time (t_s) is measured as the 10% points of the output voltage waveform at A; or as the 10% to 90% points of the magnetic flux waveform at B.

Values of S_w obtained from output voltage are about 1.5 times greater than those obtained from magnetic flux measurements. Because a preferred method has not been established, the technique of measurement should always be specified.

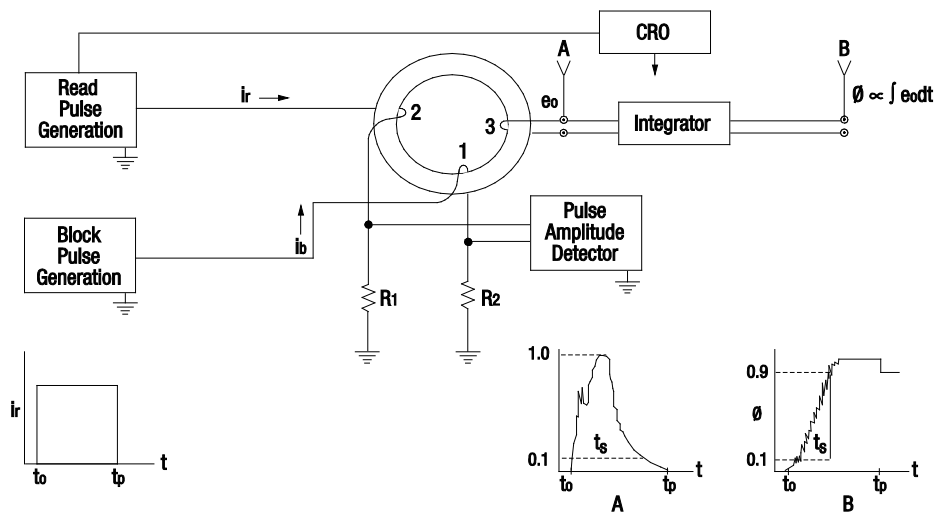

K124

Figure 1. Typical Equipment Setup Diagram

Measurement

The dependence of the switching time on the magnetizing field ($H = Ni_r/l_m$, where l_m is the mean toroid circumference) is most clearly presented by plotting $1/t_s$, as a function of H . When this is done, a linear curve is obtained, as shown in Figure 2. The experimental relationship may be adequately represented by the following equation:

$$S_w = t_s (H - H_0) \tag{1}$$

Where:

S_w = Constant for a given ferrimagnet.

t_s = Switching time.

H = Magnetizing field.


H_0 = Threshold field strength.

The threshold field strength (H_0) is slightly larger than the coercive force of the ferrimagnet and may be termed the threshold for non-uniform rotation flux reversal.

In general, both S_w and H_0 decrease with increasing temperature. Typical values of S_w for rectangular loop ferrimagnets, obtained from the output voltage waveform, range between 0.5 oe and $1.5 \text{ oe} \times \mu\text{s}$. The switching coefficient (S_w) can be considered as the additional field strength in excess of the H_0 required to switch the magnetic flux between $-B_r$ and $+B_r$ in $1 \mu\text{s}$. Because of this, a small value of S_w denotes a ferrimagnet with a rapid pulse response. For materials with the same H_0 (or same coercive force), a decrease in S_w results in a faster switching time at a given H field.

Application

In the design of latching ferrite phase shifters, the digital bit geometry and speed are dictated by system requirements. The H_0 and S_w are of use to the microwave device engineer because they enter into the calculation of switching power needed to meet the system specifications.

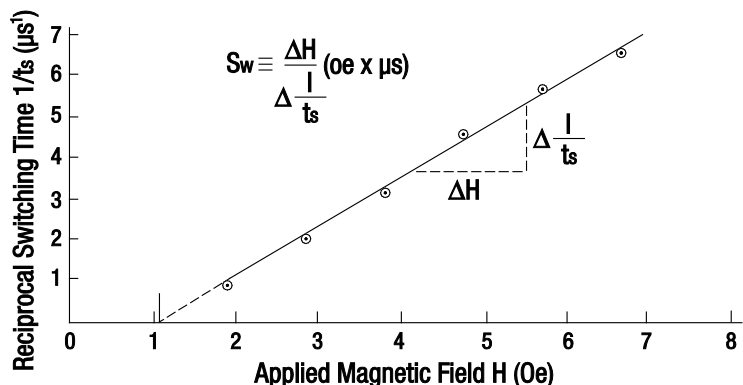

K125

Figure 2. Typical Plot of Switching Time for a Microwave Ferrimagnet Used in Digital Phase Shifters

Copyright © 2013, Trans-Tech Inc., Inc. All Rights Reserved.

Information in this document is provided in connection with Trans-Tech, Inc. ("Trans-Tech"), a wholly-owned subsidiary of Skyworks Solutions, Inc. These materials, including the information contained herein, are provided by Trans-Tech as a service to its customers and may be used for informational purposes only by the customer. Trans-Tech assumes no responsibility for errors or omissions in these materials or the information contained herein. Trans-Tech may change its documentation, products, services, specifications or product descriptions at any time, without notice. Trans-Tech makes no commitment to update the materials or information and shall have no responsibility whatsoever for conflicts, incompatibilities, or other difficulties arising from any future changes.

No license, whether express, implied, by estoppel or otherwise, is granted to any intellectual property rights by this document. Trans-Tech assumes no liability for any materials, products or information provided hereunder, including the sale, distribution, reproduction or use of Trans-Tech products, information or materials, except as may be provided in Trans-Tech Terms and Conditions of Sale.

THE MATERIALS, PRODUCTS, AND INFORMATION ARE PROVIDED "AS IS" WITHOUT WARRANTY OF ANY KIND, WHETHER EXPRESS, IMPLIED, STATUTORY, OR OTHERWISE, INCLUDING FITNESS FOR A PARTICULAR PURPOSE OR USE, MERCHANTABILITY, PERFORMANCE, QUALITY, OR NON-INFRINGEMENT OF ANY INTELLECTUAL PROPERTY RIGHT; ALL SUCH WARRANTIES ARE HEREBY EXPRESSLY DISCLAIMED. TRANS-TECH DOES NOT WARRANT THE ACCURACY OR COMPLETENESS OF THE INFORMATION, TEXT, GRAPHICS, OR OTHER ITEMS CONTAINED WITHIN THESE MATERIALS. TRANS-TECH SHALL NOT BE LIABLE FOR ANY DAMAGES, INCLUDING BUT NOT LIMITED TO ANY SPECIAL, INDIRECT, INCIDENTAL, STATUTORY, OR CONSEQUENTIAL DAMAGES, INCLUDING WITHOUT LIMITATION, LOST REVENUES OR LOST PROFITS THAT MAY RESULT FROM THE USE OF THE MATERIALS OR INFORMATION, WHETHER OR NOT THE RECIPIENT OF MATERIALS HAS BEEN ADVISED OF THE POSSIBILITY OF SUCH DAMAGE.

Trans-Tech products are not intended for use in medical, lifesaving, or life-sustaining applications, or other equipment in which the failure of the Trans-Tech products could lead to personal injury, death, or physical or environmental damage. Trans-Tech customers using or selling Trans-Tech products for use in such applications do so at their own risk and agree to fully indemnify Trans-Tech for any damages resulting from such improper use or sale.

Customers are responsible for their products and applications using Trans-Tech products, which may deviate from published specifications as a result of design defects, errors, or operation of products outside of published parameters or design specifications. Customers should include design and operating safeguards to minimize these and other risks. Trans-Tech assumes no liability for applications assistance, customer product design, or damage to any equipment resulting from the use of Trans-Tech products outside of stated published specifications or parameters.